



American  
Gear Manufacturers  
Association

---

Technical Resources

10FTM03

## **AGMA Technical Paper**

# **A Novel Approach to the Refurbishment of Wind Turbine Gears**

By M. Michaud, REM Surface  
Engineering, G.J. Sroka and  
R.E. Benson, REM Research  
Group

# **A Novel Approach to the Refurbishment of Wind Turbine Gears**

**Mark Michaud, REM Surface Engineering, Gary J. Sroka and Ronald E. Benson, REM Research Group**

[The statements and opinions contained herein are those of the author and should not be construed as an official action or opinion of the American Gear Manufacturers Association.]

## **Abstract**

Multi-megawatt wind turbine gearboxes operate under demanding environmental conditions including considerable variation in temperature, wind speed, and air quality. It is not uncommon for gearboxes rated for a maintenance free 20-year lifespan to fail after only a few years. These gearboxes experience several types of repairable damage including micropitting or “gray staining”, abrasive wear, foreign object debris (FOD) damage, surface corrosion and fretting corrosion. Wear is greatest on the input stage, especially on the sun pinion gear. Historically, grinding is utilized to refurbish these damaged gears. However, there are numerous drawbacks including but not limited to high capital investment and the extraordinary amount of time and skill involved in the grinding process. Moreover, nitrided gears cannot be ground and must be scrapped. However, chemically accelerated vibratory finishing, or isotropic superfinishing (ISF), represents a value adding, low-cost option for refurbishing both case carburized and nitrided gears. Isotropic superfinishing removes light to moderate gear flank surface damage. The result is a surface with a non-directional pattern with a roughness of approximately 0.08 mm or less. Moreover, evidence suggests that isotropic superfinishing imparts a finish that increases gear durability and service life in the field. A case study on a sun pinion gear is presented.

Copyright © 2010

American Gear Manufacturers Association  
1001 N. Fairfax Street, Suite 500  
Alexandria, Virginia, 22314

October 2010

ISBN: 978-1-55589-978-3

# A Novel Approach to the Refurbishment of Wind Turbine Gears

Mark Michaud, REM Surface Engineering, Gary J. Sroka and Ronald E. Benson, REM Research Group

## Introduction

Typical multiple megawatt (MW) gearboxes, 1.5 MW and higher, are designed to operate for 20 years without requiring major maintenance to the drive train. However, many owners are experiencing gearbox failures after only a few years of service. Gearbox repairs may cost \$360,000 (USD) or more for a complete replacement by 2009 estimates [1]. Gears fail for several reasons. Wind turbine gears operate under extreme environmental conditions including highly variable temperature, wind speeds and air quality. These conditions cause variable high loading and torque. During periods of low or no wind, the loading on slowly moving or stationary gears is exacerbated. Moreover, moisture can contaminate the lubricant and condense on the gear surfaces forming sludge, corrosion and micropitting. Finally, dust and other foreign debris in the air can contaminate the lubricant during maintenance leading to abrasive wear. Fortunately condition monitoring systems allow gearbox problems to be discovered before serious gear damage occurs [2, 3].

## Background

Wind turbine gears experience several types of repairable damage including micropitting or “gray staining”, abrasive wear, foreign object damage (FOD), surface corrosion and fretting corrosion. An example of each is depicted in Figure 1 [4, 5]. There are three main approaches to repairing gear damage: refurbishment by regrinding, refurbishment by surface finishing or replacement with a new gear. The refurbishment process is a combination of reclamation and reconditioning of a used gear or bearing [6]. New gearing is expensive which makes surface finishing and regrinding the preferred low cost alternatives. Regrinding is necessary when lead and profile corrections are required on the working surfaces of the gear teeth [7].




Figure 1a. Micropitting or gray staining on gear flanks




Figure 1b. Heavy abrasive wear on gear flank and a SEM image of trail left by an abrading particle [4]



Figure 1c. Foreign object debris (FOD) damage

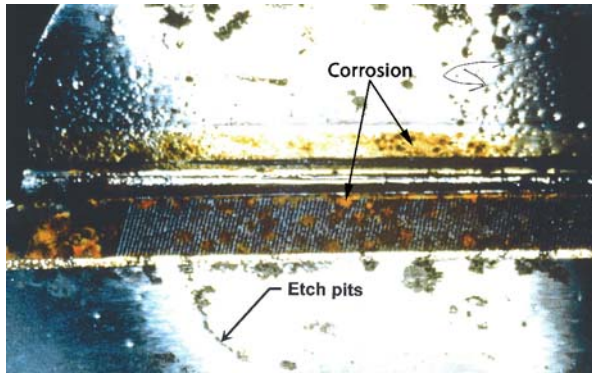

**Figure 1d. Corrosion looking down on top land [4]**

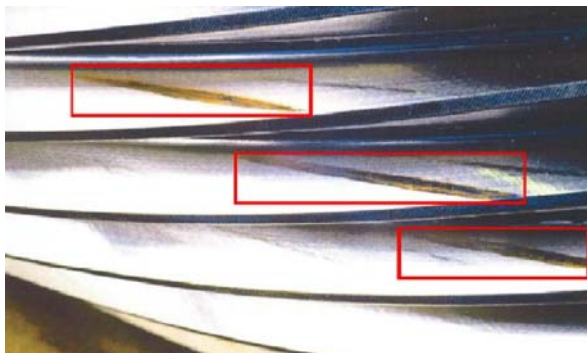


**Figure 1e. Fretting corrosion [4]**

The Isotropic Superfinish or ISF<sup>®</sup> Process, henceforward referred to as superfinishing, is an alternative time and cost efficient method of gear refurbishment. The process utilizes conventional vibratory finishing equipment and high density, nonabrasive finishing media to produce isotropic surface finishes with a final surface roughness ( $R_a$ ) below  $0.10 \mu\text{m}$ .

The superfinishing process is easily understood by referring to Figure 2. At the start of the superfinishing process shown in Step 1 of Figure 2, the original metal surface reacts a first time with the active chemistry, forming the first conversion coating (Step 2) [8]. The vibratory machine and nonabrasive media produce an effective rubbing motion on the surface of the gear (Step 3). This exposes the peak asperities of the metal surfaces to a second reaction (Step 4), re-forming the complete conversion coating. The process of conversion coating re-formation and removal (Step 5) is continued through many successive cycles thus planarizing the original rough machined or


damaged surface. The final required surface finish governs the total number of cycles. This planarizing process is continued until the gears are smoothed to the required surface finish quality. Once the required surface finish quality is achieved, the active chemistry from the smoothing stage of the superfinishing process is drained away, and a neutral, burnishing soap is introduced into the vibratory machine. The burnish removes all remaining conversion coating (Step 6) from the surface of the gear, producing a mirror-like appearance, while imparting a mild rust preventive to the surface. The gear is ready for unloading and the superfinishing process is complete. Figure 3 shows a comparison of a ground gear surface versus a superfinished gear surface.

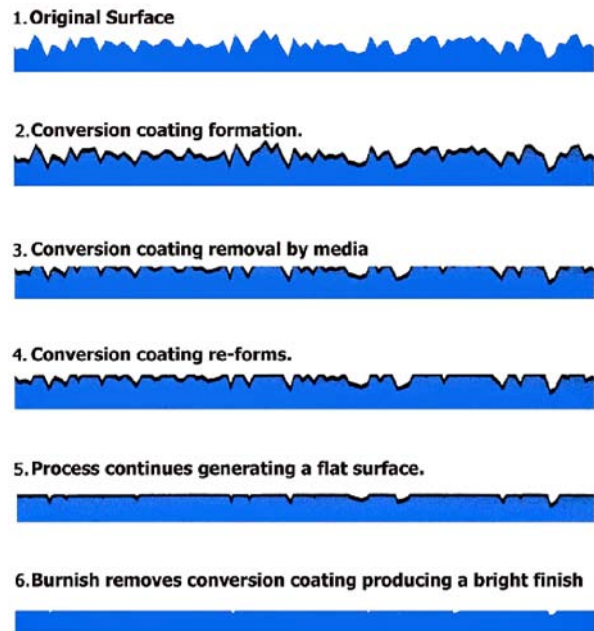

**Figure 2. Superfinishing process**

The initial selection of the proper media shape, size, and mixture is a significant part of the art to successfully superfinishing gears. Media is specifically chosen based on the following criteria:

- Root diameter
- Diametral pitch
- Gear size
- Gear mass
- Alloy

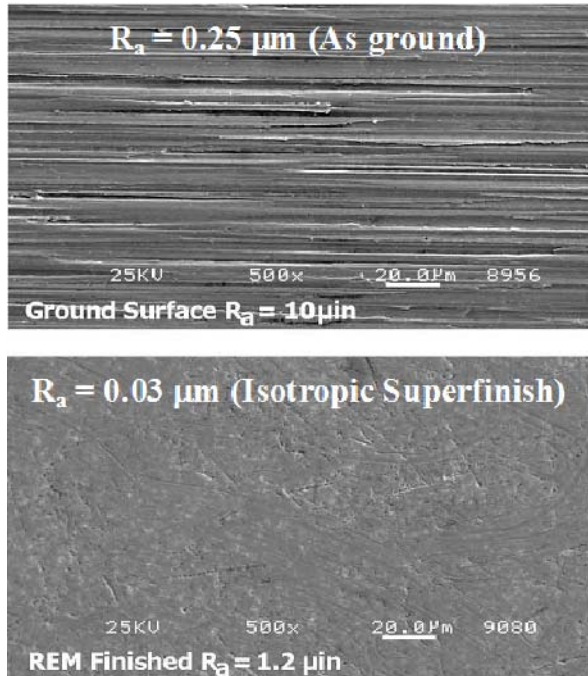

**Figure 3. Ground surface (top) versus an Isotropic Superfinish surface (bottom)**


Once the media is chosen, the superfinishing process repeatedly finishes gears identically. The media is nonabrasive, and therefore has a very low attrition rate. The size, shape, and density of the media remain stable over thousands of hours of vibratory machine operation.

The superfinishing process possesses several ideal features.

1. Superfinishing removes metal uniformly from every tooth of the gear with the ability to control total stock removal down to below 2.50  $\mu\text{m}$ .
2. There is no discoloration or temper burn, a risk that is associated with grinding.
3. Superfinishing does not destroy residual compressive stress surface layers [9]. Residual compressive stress is imparted on the surface during case hardening. Compressive stress slows the rate of surface wear and inhibits corrosion [10]. Hence, the superfinished gear exhibits a superior surface versus used gears that are refurbished by grinding.
4. The process works on nitrided as well as case carburized surfaces.
5. The superfinishing process is an ideal technique for improving the inspection of refurbished


<sup>1</sup> Maximum removal amount is per customer specifications.

gears. There is sufficient material removal to reveal subsurface damage from micropitting, scuffing and corrosion that may be masked by the texture of the used surface. Grinding and in-service wear may cause a “smearing” of the metal on the gear surface resulting in subsurface damage not only being invisible to the naked eye, but also potentially going undetected by other inspection methods [11]. For example, Figure 4 depicts a cracked gear tooth that was delivered by a customer and deemed suitable for refurbishment. Only after superfinishing did the crack become visible. Consequently, this gear was scrapped and the potential catastrophic failure of the gearbox was avoided. In general, superfinishing can.

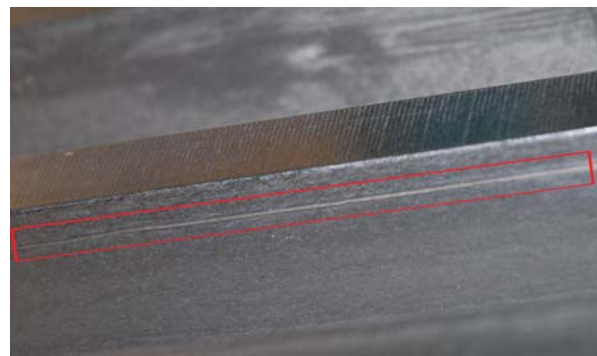

**Figure 4. Crack on a used gear near the addendum of the tooth was revealed only after superfinishing**

6. Superfinishing can also remove light ( $\leq 25 \mu\text{m}$  depth) to moderate ( $\leq 130 \mu\text{m}$  depth) damage from the gear tooth surface while maintaining geometric tolerances. Figure 5 shows images of the graphite tape lift method that is used to measure and record the amount of micropitting on a gear flank [12]. The deepest micropitting damage is approximately 150  $\mu\text{m}$  (see arrows). In this instance, it is apparent that some micropitting remains after superfinishing. The removal of all damage may have compromised the geometry of the gear. However, the peak asperities or “stress raisers” were removed and the existing micropitting will, in all likelihood, not progress to pitting and eventual spalling [13]. Recently, gearbox manufacturers indicated between 150-250  $\mu\text{m}$  can be safely removed without compromising the gear geometry.<sup>1</sup>

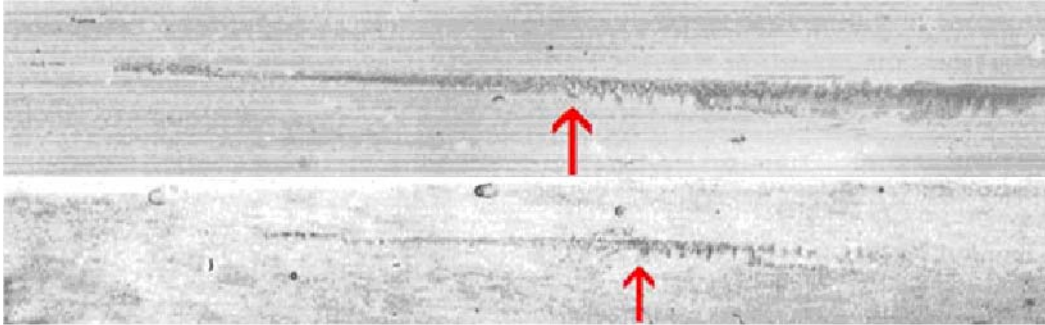

**Figure 5. Graphite tape lifts from damaged gear surface before (top) and after (bottom) superfinishing refurbishment**

Gear refurbishment via superfinishing was evaluated for bending fatigue, contact fatigue, and scoring resistance tests on military helicopter gears by the Gear Research Institute (GRI) [14, 15]. Importantly, GRI results suggest that “in all three

tests, the repaired gears met or exceeded the performance of the new gears”. Figure 6 depicts profilometer traces of (a) new ground gear, (b) used gear prior to refurbishment and (c) used gear after refurbishment via superfinishing.

HOMMELWERKE  
Turbo Datawin-NT 1.48  
Measuring conditions  
Assessment length  
Lc (Cut Off)  
Lc / Ls:

4.80 mm  
0.800 mm  
300

Ra 0.88  $\mu\text{m}$   
Rz 5.28  $\mu\text{m}$   
Rmr(0.400 $\mu\text{m}$ ) 10.3 %




**Figure 6a. Surface trace of a new ground low-speed stage pinion before superfinishing (2282)**


HOMMELWERKE  
Turbo Datawin-NT 1.48  
Measuring conditions  
Assessment length  
Lc (Cut Off)  
Lc / Ls:

4.80 mm  
0.800 mm  
300

Ra 0.71  $\mu\text{m}$   
Rz 4.31  $\mu\text{m}$

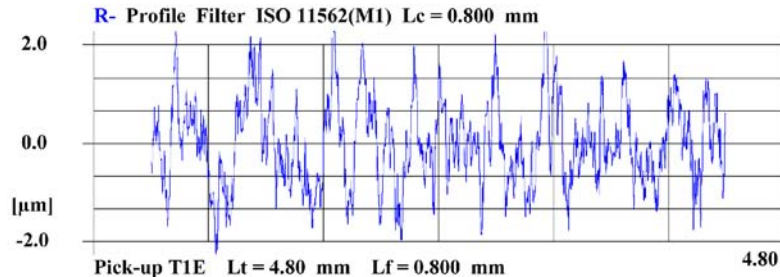

**Figure 6b. Surface trace of a used low-speed stage pinion before superfinishing (2308)**

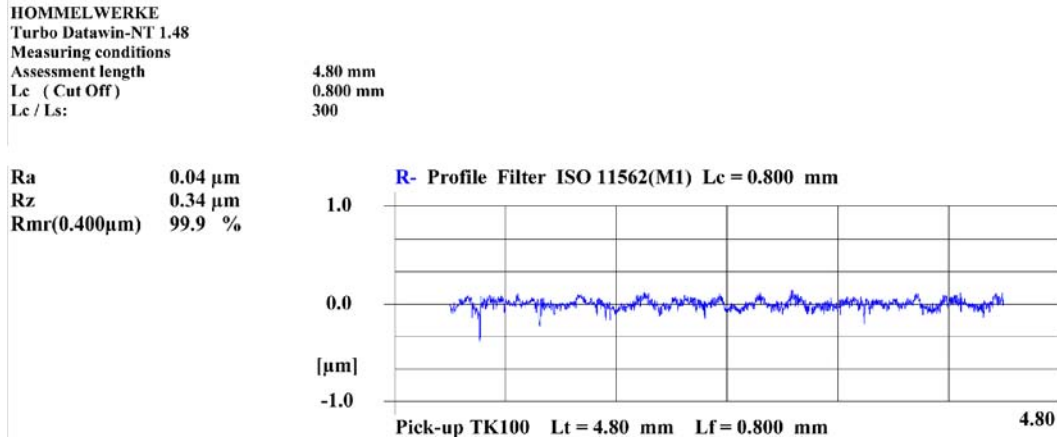

**Figure 6c. Surface trace of low-speed stage pinion after superfinishing (2282)**

Superfinishing has several distinct advantages over regrinding in terms of time and cost savings.

1. The process does not require engineering drawings.
2. All teeth are uniformly and simultaneously finished. For example, the cost per tooth is the same for a small gear with 59 teeth versus a large gear with 113 teeth.
3. As described superfinishing requires less setup time and potential complications versus grinding. Consequently, the turnaround time is rapid.
4. Typically the ring, sun and pinion gears of the low-speed stage and the output pinions of the high speed stage receive the most wear and are refurbished. However, the gears of the intermediate stage especially an assembled intermediate unit also can be superfinished with little additional expense since the entire gearbox is removed for maintenance. Figure 7 depicts a refurbished assembled intermediate stage gear.

### Case study

A case study was performed on the input stage of a 1.5 MW wind turbine gearbox. The low-speed sun pinion gear usually shows the most damage and will be used here to describe the superfinishing refurbishment process. It should be noted that customers frequently request complete refurbishment of the planetary gears and hollow wheel gear as well. The sun pinion gear is shown in Figure 8a and Figure 8b.




**Figure 7a. Superfinished intermediate gear assembly**  
(photo courtesy of Moventas)



**Figure 7b. Characteristic Isotropic Superfinish on the flanks of the intermediate gear assembly pictured above**  
(photo courtesy of Moventas)



**Figure 8a. Sun pinion gear with several modes of damage including hard line micropitting**

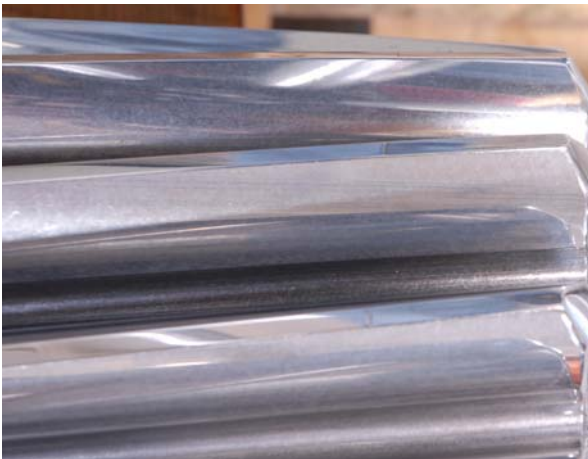

**Figure 8b. The same sun pinion gear after refurbishment**

The following protocol was used to refurbish this pinion gear:

1. After the gear was received it was inspected for damage. Micropitting and light abrasive wear were noted. Pre-finishing inspection is crucial as gears may be damaged during decommissioning and/or transport.
2. The initial average surface roughness ( $R_a$ ) was measured to be  $0.31 \mu\text{m}$ . Refer to Table 1.
3. The gear was placed in a vibratory finishing apparatus with an optimized media mixture to effect uniform stock removal on the flank.

4. It was processed in active chemistry for a short duration and then carefully inspected for hidden serious damage such as cracks or deep pitting. No serious damage was detected.
5. The gear was further processed in active chemistry and its surface roughness was periodically monitored with a skidded portable profilometer<sup>2</sup> until the targeted  $R_a$  was achieved.
6. The pinion was then burnished to remove all traces of the conversion coating.
7. The  $R_a$  of the superfinished refurbished gear was determined to be  $0.07 \mu\text{m}$ . Refer to Table 2.

**Table 1.  $R_a$  and  $R_z$  measurements taken at different locations on the sun pinion prior to refurbishment**

Trace	$R_a$ ( $\mu\text{m}$ ) Initial	$R_z$ ( $\mu\text{m}$ ) Initial
1	0.34	1.95
2	0.29	2.12
3	0.32	2.19
4	0.29	1.55
<b>Average</b>	<b>0.31</b>	<b>1.95</b>
SD	0.02	0.29

**Table 2. Four  $R_a$  and  $R_z$  measurements taken at different locations on the sun pinion after refurbishment**

Trace	$R_a$ ( $\mu\text{m}$ ) Final	$R_z$ ( $\mu\text{m}$ ) Final
1	0.06	0.46
2	0.06	0.44
3	0.07	0.50
4	0.07	0.50
<b>Average</b>	<b>0.07</b>	<b>0.48</b>
SD	0.01	0.03

## Results and discussion

In the Case Study discussed above, the planet and hollow wheel (ring) gears were also successfully refurbished. Customers utilize CMM to determine if the gears are still within tolerances after the parts are returned. All gears, more than 2300 refurbished to date, remain within the required tolerance. In the majority of cases, all traces of micropitting and other

<sup>2</sup> A Hommel T1000 Basic with a skidded T1E probe and a  $5 \mu\text{m}$  stylus was used for the case study. The profilometer is calibrated to the ISO 5436 standard.



moderate tooth damage can be successfully removed with superfinishing. Even if the micropitting is too deep to remove completely, the peak asperities or “stress raisers” are removed and micropitting will not progress to pitting and eventual spalling. Moreover, superfinishing will remove the raised lip around the lip of a FOD dent even if the valley of the damaged area is not completely removed. Gears with severe subsurface micropitting or in need of tooth profile correction must be reground first. However, it is still advantageous to use superfinishing as the final step in order to impart a much longer service life. Ongoing field tests, now more than two years old, are being conducted to corroborate that superfinished wind turbine gears have equivalent or superior performance versus new ground gears. Currently, refurbishing wind turbine gears via superfinishing is in commercial operation as a viable replacement to regrinding by a major wind turbine gearbox manufacturer.

## Conclusions

In terms of time, cost, and in-service performance superfinishing has several distinct advantages.

- The majority of damage sustained on in-service gears in wind turbine gearboxes can be successfully refurbished by superfinishing.
- Superfinishing is time efficient and economical.
  - All teeth are finished simultaneously versus a few teeth at a time.
  - Large gears finish in the same amount of time as small gears.
  - Proprietary drawings or expensive reverse engineering is not required.
  - Nital etch inspection is unnecessary.
  - The equipment:
    - ◆ Inexpensive versus regrinding;
    - ◆ Setup is simple and does not require extensive operator training
- Typically the ring, sun and pinion gears of the low-speed stage and the pinion gears of the high speed stage that acquire the most wear are refurbished. However, the gears of the intermediate and assembled intermediate stage can be refinished with little additional expense since the entire gearbox must be removed for maintenance.
- Superfinishing can reveal pre-existing sub-surface damage concealed by grinding or in-service wear related smearing.
- Previous studies by independent sources indicate that refurbishment of used gears by superfinishing results in extended operational life and reduced maintenance costs.
- When regrinding may be the only way to remove the deep damage and reshape tooth geometry, superfinishing afterwards will result in more durable surfaces and, hence, a gearbox with greater longevity in the field.

## References

1. Proactive Service Pays Dividends, *Windpower Monthly News Magazine* (Supplement), May 2009. <http://www.windpower-monthly.com>
2. Dinwiddie, K., Operations & Maintenance Real World Solutions. Presented at the STLE 65th Annual Meeting and Exhibition Wind Turbine Tribology I, May 2010.
3. Juggling with Failure as an Option, *Windpower Monthly News Magazine*, May 2008. <http://www.windpower-monthly.com>
4. Errichello, R., Technical Training Seminars: Gear Failure Analysis, American Gear Manufacturers Association, 2007.
5. Franke, J.-B., Grzybowski, R., Lifetime Prediction of Gear Teeth Regarding to Micropitting in Consideration of WEC Operating States. Presented at DEWEK 2004: The International Technical Wind Energy Conference.
6. Flowers, K., Bearing Repair Provides Valuable Alternative to Bearing Replacement for Heavy Industries, *Iron & Steel Technology*, 2009, 6 (6), 85-89.
7. Schmid, R., Process for the Modification of Tooth Traces and/or for the Correction of Tooth Trace Deviations of a Gear, United States Patent 6,752,695 B2, May 22, 2004.
8. Arvin, J., Manesh, A., Michaud, M., Sroka, G., Winkelmann, L., The Effect of Chemically Accelerated Vibratory Finishing on Gear Metrology, American Gear Manufacturers Association, 2002.
9. Dini, J.W., Fundamentals of Chemical Milling, *Am. Mach.*, 1984, 128, 113-128.
10. Lynwander, P., *Gear Drives Systems*, Marcel Dekker: New York, 1983.

11. Astakhov, V. P., *Surface Integrity in Machining*, Ed. J. P. Davim. Springer: 2010; pp. 1-35.
12. McNiff, B., Errichello, Musial, W., Documenting the Progression of Gear Micropitting in the NREL Dynamometer Test Facility, AWEA, 2002.
13. Michaud, M., Summers, E., Superfinishing Large Planetary Gear Systems, European Patent EP1646477, April 29, 2009.
14. Rao, Suren B., Repair of CH-46 Helicopter Gears, Journal of the Reliability Information Analysis Center, First quarter, 2007.
15. Rao, S., McPherson, D., Sroka, G., Repair of Helicopter Gears, American Gear Manufacturers Association, 2005.

### **Further reading**

1. Guidelines for Design of Wind Turbines. Copenhagen: Det Norske Veritas, 2002.
2. Spinato, F., Tavner, P.J., van Bussel G.J.W., Koutoulakos E., Reliability of wind turbine sub-assemblies, IET Renew. Power Gener., 2009, Vol. 3, Iss. 4, pp. 1–15.
3. Puigcorbe, J., de-Beaumont, A., Wind Turbine Gearbox Reliability: The Impact of Rotor Support, Renewable Energy World, June 2010.
4. Sawyer's Turbomachinery Maintenance Handbook, Vol. 3, Ch. 11, Turbomachinery International Publications, 1980.